

# Schomburg GmbH & Co. KG

Central application engineering, cert. WPK-Test Centre, Building material laboratory  
D – 32760 Detmold, Aquafinstr. 2-8 - Tel. 5231 / 953-247

---

## Study report 20/20 part 3

**Task:** Determination of the resistance of applied ASODUR-SG3-superfast on concrete substrates against negative water pressure according to DIN EN 12390-8

**Client:** Schomburg GmbH & Co KG - M. Hölscher

**Test date:** October-November 2020

**Official in charge:** M. Hölscher, Th. Beyer

**Materials used:**

ASODUR-SG3-superfast	Char.: 101901069
ASODUR-SG3-thix+0,5%ASO-FF	Char.: 062001101
Pavement slab 20x20 DIN EN 1339	Local building material trade

**Result:** The boards coated with ASODUR-SG3-superfast resist a water pressure of 3 bar (30m water column) maintained for 48 hours. No water penetration could be detected on the coated side. A control plate without coating showed a strong water penetration after only 30 minutes at a water pressure of 1 bar.

Detmold, 17.11.2020

  
Thomas Beyer

Head of the test centre

Execution and data in annex


## Study report 20/20 part 3

### Execution and data:

Before coating, the concrete slabs were stored in a climate of 20°C/55% relative humidity until the weight was constant.

Before coating, one of two slabs was moistened until a matt-damp substrate was created.

The coating of the panels was carried out by brushing and rolling crosswise with an area consumption of 600 g/m<sup>2</sup> on dry substrate and 450g/m<sup>2</sup> on matt-damp substrate.

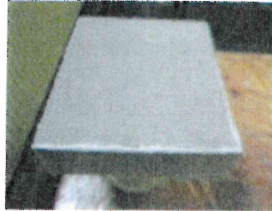

After curing of the surface, the side and bottom surfaces were coated with ASODUR-SG3-thix +0.5 % ASO-FF by brush application.



After a further storage period of 7 days in the climate, the panels were clamped in the test facility and subjected to 1 bar water pressure for 24 hours and 3 bar water pressure for 48 hours.

